

## CELANEX® 2300 GV3/20 | PBT | Glass Reinforced

### Description

Chemical abbreviation according to ISO 1043-1: PBT  
Moulding compound ISO 7792- PBT, MGHR, 08-040N, GB20

Polybutylene terephthalate, low warpage, 20 % glass beads.

Flammability UL 94 HB minimum thickness 0.82 mm.

Recognition by Underwriters Laboratories, USA (UL)

Physical properties	Value	Unit	Test Standard
Density	<b>1450</b>	kg/m <sup>3</sup>	ISO 1183
Melt volume rate (MVR)	<b>20</b>	cm <sup>3</sup> /10min	ISO 1133
MVR test temperature	<b>250</b>	°C	ISO 1133
MVR test load	<b>2.16</b>	kg	ISO 1133
Humidity absorption (23°C/50%RH)	<b>0.2</b>	%	ISO 62

Mechanical properties	Value	Unit	Test Standard
Tensile modulus (1mm/min)	<b>3500</b>	MPa	ISO 527-2/1A
Tensile stress at break (5mm/min)	<b>50</b>	MPa	ISO 527-2/1A
Tensile strain at break (5mm/min)	<b>4</b>	%	ISO 527-2/1A
Tensile creep modulus (1h)	<b>3500</b>	MPa	ISO 899-1
Tensile creep modulus (1000h)	<b>2400</b>	MPa	ISO 899-1
Flexural strength (23°C)	<b>86</b>	MPa	ISO 178
Charpy impact strength @ 23°C	<b>34</b>	kJ/m <sup>2</sup>	ISO 179/1eU
Charpy impact strength @ -30°C	<b>34</b>	kJ/m <sup>2</sup>	ISO 179/1eU
Charpy notched impact strength @ 23°C	<b>3.5</b>	kJ/m <sup>2</sup>	ISO 179/1eA
Charpy notched impact strength @ -30°C	<b>3.5</b>	kJ/m <sup>2</sup>	ISO 179/1eA

Thermal properties	Value	Unit	Test Standard
Melting temperature (10°C/min)	<b>225</b>	°C	ISO 11357-1,-2,-3
DTUL @ 1.8 MPa	<b>70</b>	°C	ISO 75-1/-2
DTUL @ 0.45 MPa	<b>180</b>	°C	ISO 75-1/-2
Vicat softening temperature B50 (50°C/h 50N)	<b>190</b>	°C	ISO 306
Coeff.of linear therm. expansion (parallel)	<b>1.1</b>	E-4/°C	ISO 11359-2
Limiting oxygen index (LOI)	<b>21</b>	%	ISO 4589
Flammability @1.6mm nom. thickn.	<b>HB</b>	class	UL94
thickness tested (1.6)	<b>1.6</b>	mm	UL94
UL recognition (1.6)	<b>UL</b>	-	UL94
Flammability at thickness h	<b>HB</b>	class	UL94
thickness tested (h)	<b>0.82</b>	mm	UL94
UL recognition (h)	<b>UL</b>	-	UL94

Electrical properties	Value	Unit	Test Standard
Relative permittivity - 100 Hz	<b>4.4</b>	-	IEC 60250
Relative permittivity - 1 MHz	<b>4.2</b>	-	IEC 60250
Dissipation factor - 100 Hz	<b>85</b>	E-4	IEC 60250
Dissipation factor - 1 MHz	<b>180</b>	E-4	IEC 60250
Volume resistivity	<b>&gt;1E13</b>	Ohm*m	IEC 60093



**CELANEX® 2300 GV3/20 | PBT | Glass Reinforced**

Electrical properties	Value	Unit	Test Standard
Surface resistivity	>1E15	Ohm	IEC 60093
Electric strength	26	kV/mm	IEC 60243-1
Comparative tracking index CTI	225	-	IEC 60112

Test specimen production	Value	Unit	Test Standard
Processing conditions acc. ISO	7792	-	Internal
Injection molding melt temperature	260	°C	ISO 294
Injection molding mold temperature	80	°C	ISO 294
Injection molding flow front velocity	200	mm/s	ISO 294
Injection molding hold pressure	70	MPa	ISO 294


**Viscosity-shear rate**

**Shearstress-shear rate**

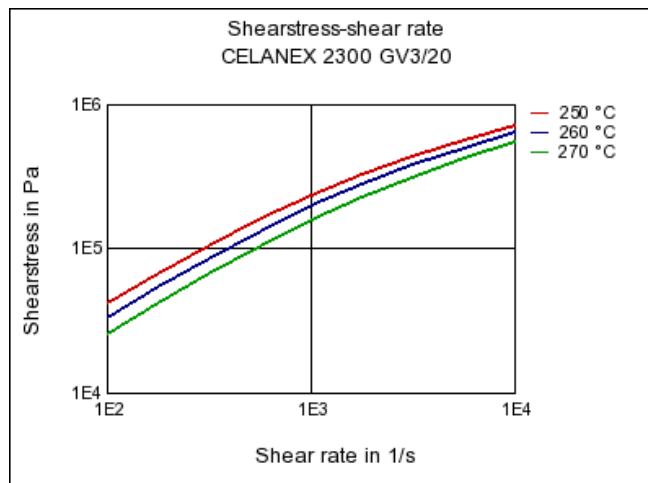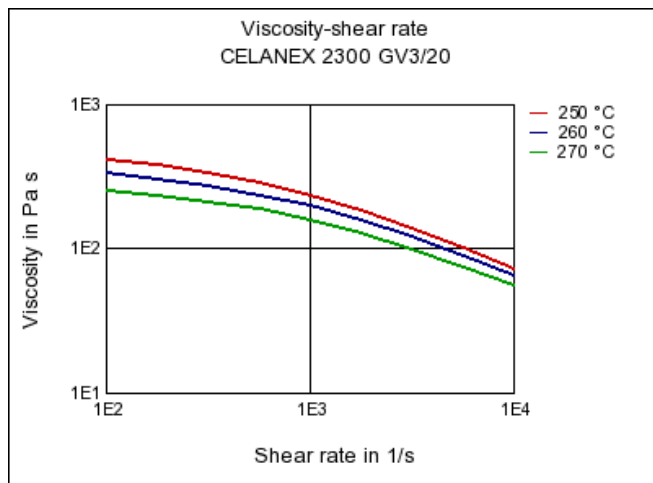


**CELANEX® 2300 GV3/20 | PBT | Glass Reinforced**


**Dynamic Shear modulus-temperature**

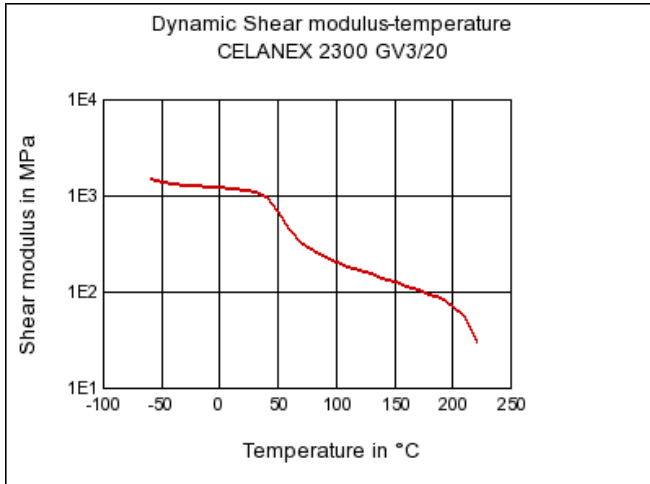

**Stress-strain**

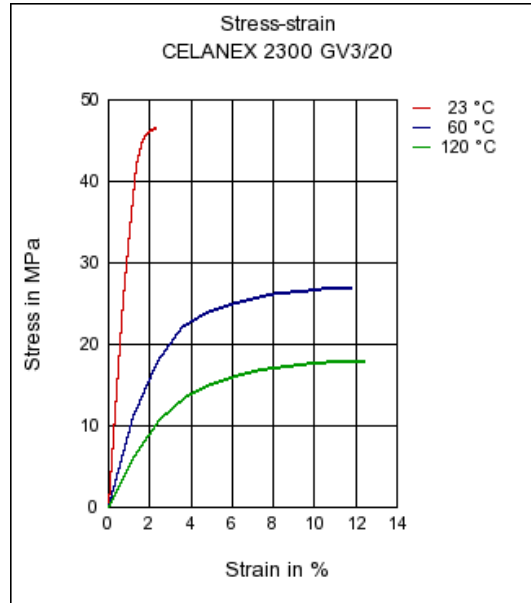


**Secant modulus-strain**

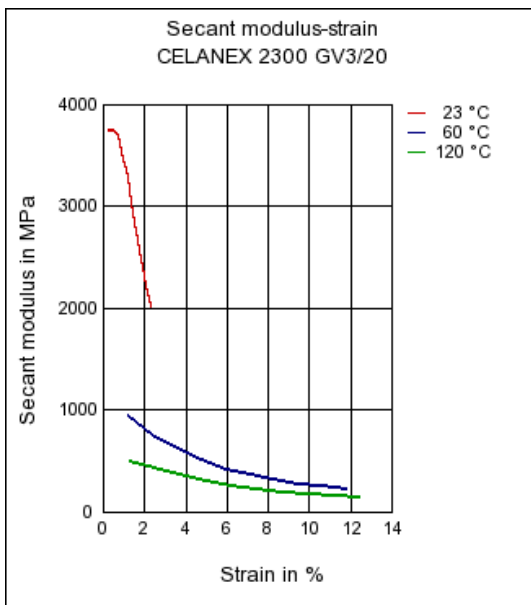

**CELANEX® 2300 GV3/20 | PBT | Glass Reinforced**

**Typical injection moulding processing conditions**

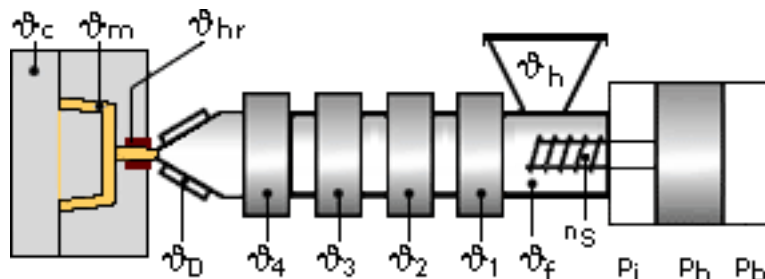

**Pre Drying:**

**Necessary low maximum residual moisture content: 0.02%**

CELANEX should in principle be predried. Because of the necessary low maximum residual moisture content the use of dry air dryers is recommended. The dew point should be  $\leq -30^{\circ}\text{C}$ . The time between drying and processing should be as short as possible.

For subsequent storage of the material in the dryer until processed ( $\leq 60$  h) it is necessary to lower the temperature to  $100^{\circ}\text{C}$ .

**Drying time: 2 - 4 h**

**Drying temperature: 120 - 140 °C**

**Temperature:**

	$\varnothing$ Manifold	$\varnothing$ Mold	$\varnothing$ Melt	$\varnothing$ Nozzle	$\varnothing$ Zone4	$\varnothing$ Zone3	$\varnothing$ Zone2	$\varnothing$ Zone1	$\varnothing$ Feed	$\varnothing$ Hopper
min (°C)	260	75	260	260	255	255	250	250	190	20
max (°C)	270	100	270	270	265	265	260	260	200	50

**Speed:**

**Injection speed: fast**

**Screw speed**

Screw diameter (mm)	16	25	40	55	75
Screw speed (RPM)	-	90	75	60	-

**Injection Molding**

Melt Temperature	260-270 °C
Mold Temperature *)	75-85 °C
Maximum Barrel Residence Time **)	5-10 min
Injection Speed	fast
Peripheral screw speed	max. 0,3 m/sec
Back Pressure	10-30 bar
Injection Pressure	600-1000 bar
Holding Pressure	400-800 bar
Nozzle Design	open design preferred

Injection speed, injection pressure and holding pressure have to be optimized to the individual article geometry. To avoid material degradation during processing low back pressure and minimum screw speed have to be used. Overheating of the material has to be avoided. For grades containing flame retardants, a maximum temperature of  $265^{\circ}\text{C}$  should not be exceeded.

## CELANEX® 2300 GV3/20 | PBT | Glass Reinforced

Ticona recommends only externally heated hot runner systems.

\*) For moulded parts with especially high requirements to the surface quality or dimensional stability, a mold temperature of up to 110 °C can be advantageous.

\*\*\*) If the cylinder temperatures are higher than the recommended maximum temperatures, the max. residence time in the barrel has to be reduced.

### Contact Information

#### Americas

Ticona North American Headquarters  
Product Information Service  
8040 Dixie Highway  
Florence, KY 41042  
USA  
Tel.: +1-800-833-4882  
Tel.: +1-859-372-3244  
email: [prodinfo@ticona.com](mailto:prodinfo@ticona.com)  
Ticona on the web: [www.ticona.com](http://www.ticona.com)

#### Customer Service

Tel.: +1-800-526-4960  
Tel.: +1-859-372-3214  
Fax: +1-859-372-3125

#### Europe

Ticona GmbH  
Information Service  
Tel.: +49 (0) 180-5842662 (Germany)  
+49 (0) 69-30516299 (Europe)  
Fax: +49 (0) 180-2021202 (Germany & Europe)  
email: [infoservice@ticona.de](mailto:infoservice@ticona.de)  
Internet: [www.ticona.com](http://www.ticona.com)

### General Disclaimer

NOTICE TO USERS: Values shown are based on testing of laboratory test specimens and represent data that fall within the standard range of properties for natural material. These values alone do not represent a sufficient basis for any part design and are not intended for use in establishing maximum, minimum, or ranges of values for specification purposes. Colorants or other additives may cause significant variations in data values.

Properties of molded parts can be influenced by a wide variety of factors including, but not limited to, material selection, additives, part design, processing conditions and environmental exposure. Any determination of the suitability of a particular material and part design for any use contemplated by the users and the manner of such use is the sole responsibility of the users, who must assure themselves that the material as subsequently processed meets the needs of their particular product or use.

To the best of our knowledge, the information contained in this publication is accurate; however, we do not assume any liability whatsoever for the accuracy and completeness of such information. The information contained in this publication should not be construed as a promise or guarantee of specific properties of our products. It is the sole responsibility of the users to investigate whether any existing patents are infringed by the use of the materials mentioned in this publication.

Moreover, there is a need to reduce human exposure to many materials to the lowest practical limits in view of possible adverse effects. To the extent that any hazards may have been mentioned in this publication, we neither suggest nor guarantee that such hazards are the only ones that exist. We recommend that persons intending to rely on any recommendation or to use any equipment, processing technique or material mentioned in this publication should satisfy themselves that they can meet all applicable safety and health standards.

We strongly recommend that users seek and adhere to the manufacturer's current instructions for handling each material they use, and entrust the handling of such material to adequately trained personnel only. Please call the telephone numbers listed (+49 (0) 69 30516299 for Europe and +1 859-372-3244 for the Americas) for additional technical information. Call Customer Services for the appropriate Materials Safety Data Sheets (MSDS) before attempting to process our products.

The products mentioned herein are not intended for use in medical or dental implants.

© Copyright 2007, Ticona, all rights reserved. (Pub. 26-September-2013)