

FORTRON® 1131L4 ITT | PPS | Glass Reinforced

| Physical properties | Value | Unit | Test Standard |
|-----------------------------|------------------|-------------------|---------------|
| Density | 1560 | kg/m ³ | ISO 1183 |
| Mold shrinkage - parallel | 0.3 - 0.7 | % | ISO 294-4 |
| Mold shrinkage - normal | 0.5 - 0.8 | % | ISO 294-4 |
| Water absorption (23°C-sat) | 0.02 | % | ISO 62 |

| Mechanical properties | Value | Unit | Test Standard |
|--|--------------|-------------------|---------------|
| Tensile modulus (1mm/min) | 12200 | MPa | ISO 527-2/1A |
| Tensile stress at break (5mm/min) | 165 | MPa | ISO 527-2/1A |
| Tensile strain at break (5mm/min) | 1.9 | % | ISO 527-2/1A |
| Flexural modulus (23°C) | 12000 | MPa | ISO 178 |
| Flexural stress @ break | 255 | MPa | ISO 178 |
| Charpy impact strength @ 23°C | 42 | kJ/m ² | ISO 179/1eU |
| Charpy impact strength @ -30°C | 42 | kJ/m ² | ISO 179/1eU |
| Charpy notched impact strength @ 23°C | 8 | kJ/m ² | ISO 179/1eA |
| Charpy notched impact strength @ -30°C | 8 | kJ/m ² | ISO 179/1eA |
| Notched impact strength (Izod) @ 23°C | 8 | kJ/m ² | ISO 180/1A |
| Notched impact strength (Izod) @-30°C | 8 | kJ/m ² | ISO 180/1A |
| Rockwell hardness | 100 | M-Scale | ISO 2039-2 |


| Thermal properties | Value | Unit | Test Standard |
|--|---------------------------|-------------|-------------------|
| Melting temperature (10°C/min) | 280 | °C | ISO 11357-1,-2,-3 |
| Glass transition temperature (10°C/min) | 90 | °C | ISO 11357-1,-2,-3 |
| DTUL @ 1.8 MPa | 265 | °C | ISO 75-1/-2 |
| DTUL @ 8.0 MPa | 205 | °C | ISO 75-1/-2 |
| Coeff.of linear therm. expansion (parallel) | 0.29 | E-4/°C | ISO 11359-2 |
| Coeff.of linear therm. expansion (normal) | 0.62 | E-4/°C | ISO 11359-2 |
| Flammability @1.6mm nom. thickn. thickness tested (1.6) | V-0 1.5 | class mm | UL94 UL94 |
| Flammability at thickness h thickness tested (h) | V-0 0.38 | class mm | UL94 UL94 |

| Electrical properties | Value | Unit | Test Standard |
|-----------------------|-----------------|-------|---------------|
| Volume resistivity | >1E13 | Ohm*m | IEC 60093 |
| Surface resistivity | >1E15 | Ohm | IEC 60093 |

| Test specimen production | Value | Unit | Test Standard |
|------------------------------------|------------------|------|---------------|
| Injection molding melt temperature | 310 - 340 | °C | ISO 294 |
| Injection molding mold temperature | 135 - 160 | °C | ISO 294 |

FORTRON® 1131L4 ITT | PPS | Glass Reinforced

Typical injection moulding processing conditions

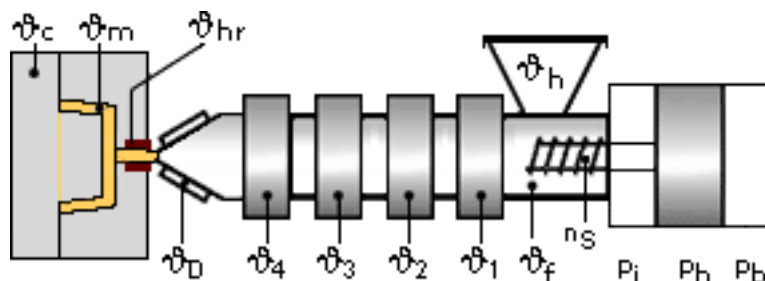

Pre Drying:

Necessary low maximum residual moisture content: 0.02%

FORTRON should in principle be predried. Because of the necessary low maximum residual moisture content the use of dry air dryers is recommended. The dew point should be $\leq -30^\circ\text{C}$. The time between drying and processing should be as short as possible.

For subsequent storage the material should be stored dry in the dryer until processed (≤ 60 h).

Drying time: 3 - 4 h

Drying temperature: 130 - 140 °C

Temperature:

| | $\varnothing_{\text{Manifold}}$ | $\varnothing_{\text{Mold}}$ | $\varnothing_{\text{Melt}}$ | $\varnothing_{\text{Nozzle}}$ | $\varnothing_{\text{Zone4}}$ | $\varnothing_{\text{Zone3}}$ | $\varnothing_{\text{Zone2}}$ | $\varnothing_{\text{Zone1}}$ | $\varnothing_{\text{Feed}}$ | $\varnothing_{\text{Hopper}}$ |
|----------|---------------------------------|-----------------------------|-----------------------------|-------------------------------|------------------------------|------------------------------|------------------------------|------------------------------|-----------------------------|-------------------------------|
| min (°C) | 330 | 140 | 330 | 310 | 330 | 330 | 310 | 290 | 60 | 20 |
| max (°C) | 340 | 160 | 340 | 330 | 340 | 340 | 320 | 300 | 80 | 30 |

Pressure:

| | Inj press | Hold press | Back pressure |
|-----------|-----------|------------|---------------|
| min (bar) | 500 | 300 | 0 |
| max (bar) | 1000 | 700 | 30 |

Speed:

Injection speed: fast

Screw speed

| | | | | | |
|---------------------|----|-----|----|----|----|
| Screw diameter (mm) | 16 | 25 | 40 | 55 | 75 |
| Screw speed (RPM) | - | 120 | 75 | 50 | - |

Contact Information

Americas

Ticona North American Headquarters
Product Information Service
8040 Dixie Highway
Florence, KY 41042
USA
Tel.: +1-800-833-4882

Europe

Ticona GmbH
Information Service
Tel.: +49 (0) 180-5842662 (Germany)
+49 (0) 69-30516299 (Europe)
Fax: +49 (0) 180-2021202 (Germany & Europe)
email: info@ticona.de

FORTRON® 1131L4 ITT | PPS | Glass Reinforced

Tel.: +1-859-372-3244
email: prodinfo@ticona.com
Ticona on the web: www.ticona.com

Internet: www.ticona.com

Customer Service
Tel.: +1-800-526-4960
Tel.: +1-859-372-3214
Fax: +1-859-372-3125

General Disclaimer

NOTICE TO USERS: Values shown are based on testing of laboratory test specimens and represent data that fall within the standard range of properties for natural material. These values alone do not represent a sufficient basis for any part design and are not intended for use in establishing maximum, minimum, or ranges of values for specification purposes. Colorants or other additives may cause significant variations in data values.

Properties of molded parts can be influenced by a wide variety of factors including, but not limited to, material selection, additives, part design, processing conditions and environmental exposure. Any determination of the suitability of a particular material and part design for any use contemplated by the users and the manner of such use is the sole responsibility of the users, who must assure themselves that the material as subsequently processed meets the needs of their particular product or use.

To the best of our knowledge, the information contained in this publication is accurate; however, we do not assume any liability whatsoever for the accuracy and completeness of such information. The information contained in this publication should not be construed as a promise or guarantee of specific properties of our products. It is the sole responsibility of the users to investigate whether any existing patents are infringed by the use of the materials mentioned in this publication.

Moreover, there is a need to reduce human exposure to many materials to the lowest practical limits in view of possible adverse effects. To the extent that any hazards may have been mentioned in this publication, we neither suggest nor guarantee that such hazards are the only ones that exist. We recommend that persons intending to rely on any recommendation or to use any equipment, processing technique or material mentioned in this publication should satisfy themselves that they can meet all applicable safety and health standards.

We strongly recommend that users seek and adhere to the manufacturer's current instructions for handling each material they use, and entrust the handling of such material to adequately trained personnel only. Please call the telephone numbers listed (+49 (0) 69 30516299 for Europe and +1 859-372-3244 for the Americas) for additional technical information. Call Customer Services for the appropriate Materials Safety Data Sheets (MSDS) before attempting to process our products.

The products mentioned herein are not intended for use in medical or dental implants.

© Copyright 2007, Ticona, all rights reserved. (Pub. 26-September-2013)